



# Superhydrophobic Treatment of Polyurethane Sponge and Its Application in Oil-water Separation

Fan Li<sup>1</sup>, Wenhong Wang<sup>1</sup>, Jie Wang<sup>1</sup> and Yangfeng Peng<sup>1\*</sup>

<sup>1</sup>*School of Chemical Engineering, East China University of Science and Technology, Shanghai 200237, China.*

## **Authors' contributions**

*This work was carried out in collaboration among all authors. Author FL designed the study, performed the investigation and wrote the first draft of the manuscript. Authors WW and JW helped to analyze the results and revised the manuscript. Author YP supervised the study and revised the manuscript. All authors read and approved the final manuscript.*

## **Article Information**

DOI: 10.9734/AJOCS/2019/v6i419004

### Editor(s):

(1) Dr. Fahmida Khan, National Institute of Technology, Raipur, India.

### Reviewers:

(1) Ioannis Karapanagiotis, University Ecclesiastical Academy of Thessaloniki, Greece.

(2) A. Ayeshamariam, India.

Complete Peer review History: <http://www.sdiarticle4.com/review-history/53185>

**Original Research Article**

**Received 06 October 2019**  
**Accepted 11 December 2019**  
**Published 18 December 2019**

## **ABSTRACT**

The superhydrophobicity of the polyurethane sponge was realized by attaching the complex of copper and mercaptan on the outer surface of the polyurethane sponge. As a special case, the complex of 1-dodecanthiol and copper chloride was intensively investigated in this study, with emphasis on the influences of concentration, temperature and residence time on the reaction. SEM and EDS were used to analyze the surface structure and elemental composition of the sponge. The superhydrophobicity of the sponge are contributed by the rough treatment on sponge surface. It is found that a large number of long carbon chains appear on the surface reduces the surface energy. The wettability of the surface was determined by a contact angle meter. The material demonstrates great oil-water separation performance and high repeatability in superhydrophobicity during the the separation process of oil and water before first 39 times.

**Keywords:** Superhydrophobicity; polyurethane sponge; oil/water separation; wettability.

\*Corresponding author: E-mail: [yfpeng@ecust.edu.cn](mailto:yfpeng@ecust.edu.cn);

## 1. INTRODUCTION

With the continuous development of industry and agriculture, the consumption of petroleum and other energy products has been increasing [1]. The environmental pollution [2] caused by the leakage of oil products is becoming increasingly serious [3]. The oil spill accidents reported in recent years have resulted in a spate of water pollution [4]. A variety of treatment technologies, including physical, chemical and biological [5,6,7] methods have been developed for the treatment of contaminated water. Physical method is simple but has low efficiency. Both chemical and biological methods require adding chemical reagents in polluted water sources, which can pose a high risk of secondary pollution. With the emergence and development of new materials [8], efficient oil-water separation materials [9] have gained increasing attention in recent years for the treatment of contaminated water [10,11], given its unique advantages of high efficiency and no pollution [12].

The understanding of the superhydrophobic surface [13] originates from some plants and animals in nature [14]. They are waterproof, antifouling, reducing resistance and so on [15,16]. There are differences in the way superhydrophobic surfaces are constructed, but there are two main steps: (1) Construct a rough surface (2) Modified with low surface energy substances.

Polyurethane sponge [17] as the basis of materials [18], shows great advantages in practical application since it has the characteristics of high porosity, low cost and excellent stability [19,20,21,22].

In this experiment, the compounds of mercaptan and bivalent copper [23,24] were prepared and then covered in the surface of PU sponge [25], so that the sponge had the superhydrophobicity. It is also found that superhydrophobic sponge has excellent performance in oil and water separation [26].

## 2. EXPERIMENTAL

### 2.1 Reagents

High-density sponge, 200-400  $\mu\text{m}$ ; Medium-density sponge, 330-480  $\mu\text{m}$ ; Low-density sponge, 700-850  $\mu\text{m}$ , all sponges were bought from Nanjing Yongsheng sponge factory; Sodium hydroxide, AR; Copper chloride, AR; Decyl

mercaptan, AR; 1-Dodecanethiol, AR; 1-Octadecanethiol, AR; Sudan Red, AR; Dimethylbenzene, AR; Ethanol, AR; All reagents were bought from Shanghai Taitan Technology.

### 2.2 Preparation of Superhydrophobic Sponge

First, the sponge (2 cm $\times$ 2 cm $\times$ 1 cm) was washed with sodium hydroxide solution for 15 min to remove the grease from the sponge, and then deionized water was used for ultrasonic washing for 15 min, drying and waiting. In the ratio of 4:1, the temperature is 30 $^{\circ}\text{C}$ , the time is 8 min, and the pH is 8, and the reaction of 1-dodecanthiol and copper chloride is precipitated. By dispersing dry solid ultrasound into ethanol, the dispersion of 8 mg mL $^{-1}$  was obtained. The clean PU sponge was added to the dispersion solution, and the ultrasound was used for 15 min, drying and obtaining the product. The treatments were similar to the preparation of the superhydrophobic sponge using decyl mercaptan or 1-octadecanethiol.

### 2.3 Characterization

The surface morphology and structure of the samples were analyzed by scanning electron microscopy (S-3400 N, Hitachi, Japan). The composition of the sample was quantified using an energy spectrometer (ESCALAB 250 xi, Thermo Fisher Scientific, USA). The wettability of the sample was analyzed by static contact angle meter (YIKE - 360 A, Chengde Yike, China). The droplets were distilled water, and the water volume was 3  $\mu\text{L}$ , the droplets were discontinuous. In order to ensure the reliability of the experiment, five different areas were selected for the surface of the sample.

## 3. RESULTS AND DISCUSSION

### 3.1 The Influence of the Ratio of Mercaptan to Copper Chloride

The weight of copper chloride was controlled at 1g, the complexes were prepared, the ratio of 1-dodecanthiol to copper chloride was 1:2, 1:1, 2:1, 3:1, 4:1, 5:1. Fig. 1 shows the variation of weight with proportion. When the ratio of mercaptan to copper chloride was 4:1, the weight of the product was the largest. It was observed that the color of final solution was blue when the ratio was less than 4:1 and the solution is colorless at 4:1. The experiment found that when the ratio was greater than 4:1, a large amount of mercaptan was wrapped by the product, which

resulted in a decrease in weight. After the complexes were attached to the sponge, the water contact angle on the sponge was determined. Fig. 2 shows the relationship between the water contact angle and the ratio. The maximum standard deviation of the contact angles in this investigation is 2.3 and the average standard deviation is 1.8. The results show that the contact angle has weak relation with the ratio. EDS analysis showed that the ratio of mercaptan to copper in the complexes was n:1 and the proportion of each product was distributed.

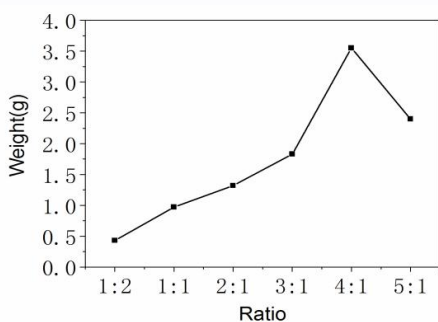


Fig. 1. The influence of the ratio on the weight

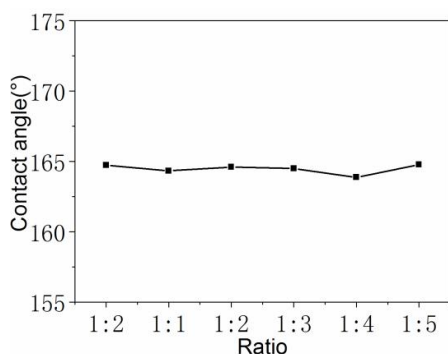


Fig. 2. The influence of the ratio on water contact angle

### 3.2 The Influence of Temperature on the Weight

The temperature is an important influence factor in most chemical reactions. In order to determine the optimal condition, the reaction temperature was controlled to obtain its relationship with the product weight, as shown in Fig. 3. The weight of complex increased slowly with the increase of temperature when below 30°C, and became stable when above 30°C. In general, little influence has been found of temperature in the product weight. Which is caused by a high reaction rate. The optimal reaction temperature is found to be 30°C.

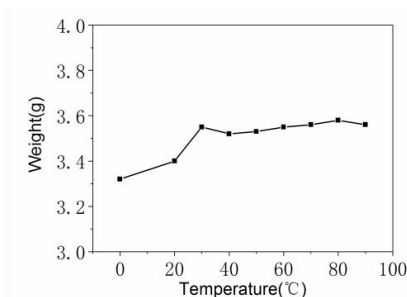


Fig. 3. The influence of temperature on the weight of products

### 3.3 The Influence of Reaction Time on the Weight

The reaction time is another important factor in chemical reactions. In order to explore the influence of reaction time on the product weight, the weight of the product at different times was measured to determine the optimal time. The reaction of complex was enhanced by applying ultrasonic at 50 kHz. According to the Fig. 4, the product weight increased with the reaction time at first 7 mins and reached plateau afterwards. So the optimal reaction time is found to be 8 min.


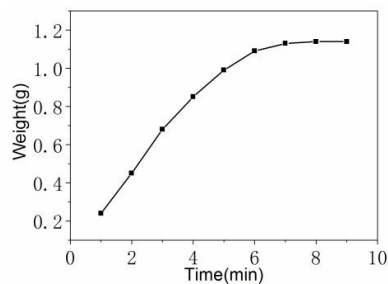


Fig. 4. The influence of reaction time on the weight of the product

### 3.4 The Influence of pH on the Weight

The pH would affect the ionization of mercapto group in solution and then the forming of complex. The influence of pH on the product weight was explored. Fig. 5 shows the relationship between the pH and the product weight. The weight was almost the same as the pH were 2 and 4, then the weight increased sharply with the rise of pH and reached the maximum value at the pH of 8. When the pH of the reaction is less than 8, the degree of -SH ionization in dodecanethiol is limited [27]. There are a small amount of thiols that can be coordinated with copper ions and only little

complex forms as the pH of reaction is less than 8. When pH >8, the weight decreased rapidly, which can be explained by that a large amount of copper precipitated in the form of copper hydroxide.

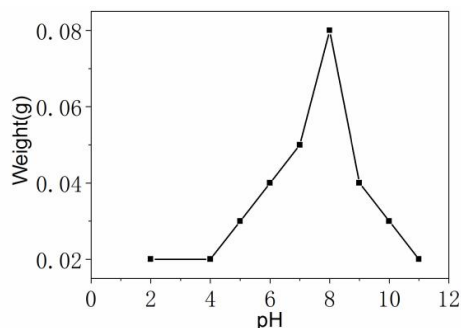

**Fig. 5. The influence of the pH on the weight**

### 3.5 The Influence of Concentration on Wettability


As shown in Fig. 6 A, the pristine sponge is not hydrophobic with the water contact angle of  $93^\circ$ , the hydrophobicity of sponge could be developed by the method indicated in 3.1-3.4 and 2.2. Here, the influence of the concentration of complex in suspension on the wettability was explored. The results are shown in Fig. 7. The maximum standard deviation of the contact angles in this investigation is 3.6 and the average standard deviation is 1.9., the water contact angle on the sponge rises slowly from  $152^\circ$  to  $164^\circ$  with the increase of concentration of complex in suspension liquid from  $2 \text{ mg mL}^{-1}$  to  $12 \text{ mg mL}^{-1}$ . Fig. 7 also shows that the contact angle is  $147^\circ$  with the concentration of  $0.2 \text{ mg mL}^{-1}$ . The investigation found it was easy for the complex to fall out from the sponge when the concentration was higher than  $8 \text{ mg mL}^{-1}$ . The reason may be the sponge is overloaded for the complex. So the optimal concentration of complex was set at  $8 \text{ mg mL}^{-1}$ . Fig. 6 B shows

the water contact angle of  $166^\circ$  on the superhydrophobic sponge.

In order to explore the effect of the pore size on the wettability, three sponges with different pore sizes were investigated. The complex was distributed to those sponges as mentioned in 2.2, and the water contact angle on those sponges attached with complex was measured, the results are also contained in Fig. 6, the contact angles differ a little for the medium density sponge and low density sponge, the reason is considered that the size of pore for the medium density sponge and low density sponge is larger than the size of water drop, and the high density sponges with smallest size of pore show the biggest contact angle at different concentration.

### 3.6 The Influence of the Mercaptans on Wettability


The different lengths of the carbon chains for mercaptans can affect the wettability of the sponge. In this investigation, three mercaptans, decyl mercaptan, 1-dodecanethiol and 1-octadecanethiol were used because they are available in the market. The complexes of those mercaptans with copper chloride were prepared and distributed to the sponges respectively. The water contact angle on those three kinds of sponges were measured and the result is shown in Fig. 8. The maximum standard deviation of the water contact angles in this investigation is 1.7 and the average standard deviation is 1.4. According to the Fig. 8, with the increase of carbon chain for mercaptans, the contact angle on the sponge rises within for concentration of 2, 4, 6, 8  $\text{mg mL}^{-1}$ . Since 1-octadecanethiol is more expensive than 1-dodecanethiol and the water contact angle of the sponge attached with complex of 1-dodecanethiol-copper also larger than  $150^\circ$  at the concentrations showing Fig. 8. So the 1-dodecanethiol was selected.

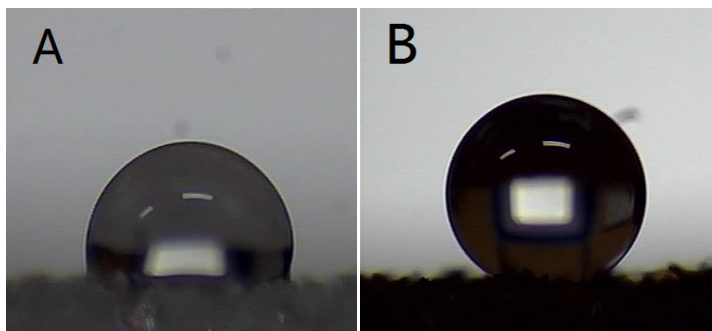

**Fig. 6. Static water contact angle on sponge before and after treatment**


### 3.7 Surface Structure of the Sponge

Fig. 9 shows the surface structure of the pristine and superhydrophobic sponge with SEM images. From Fig. 9, the pristine sponge has a smooth surface (Fig. 9. A-B) and the surface of superhydrophobic sponge is rough (Fig. 9. C-D). The solid particles produced by copper chloride and dodecyl mercaptan are attached to the surfaces of sponges resulting in the sponge's rough surface. It is believed that the roughness of surface is one of key factors for the superhydrophobicity.

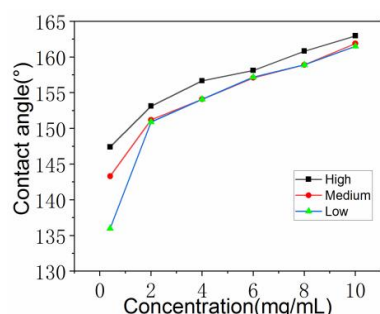

**Fig. 7. The influence of concentration on wettability**

(High - high density sponge; Medium - medium density sponge; Low - low density sponge)

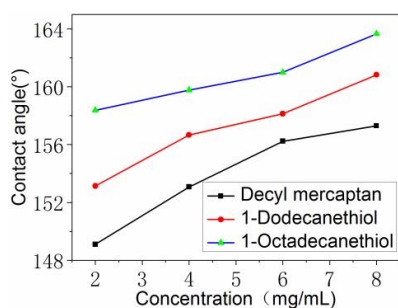

**Fig. 8. The effect of the type of mercaptan on the wettability of materials**

(Decyl mercaptan - Sponge attached by complex of decyl mercaptan with copper chloride;  
1 - Dodecanethiol - Sponge attached by complex of 1 - dodecanethiol with copper chloride;  
1 - Octadecanethiol - Sponge attached by complex of 1 - octadecanethiol with copper chloride)

### 3.8 EDS for the Surface of Sponge

To verify the complex of mercaptan and copper chloride were attached to the surface of the superhydrophobic sponge, EDS was used to identify the presence of sulfur and copper on the sponge. The result was shown in Table 1. From

the Table 1, sulfur and copper are found in the superhydrophobic sponge and their content in weight reach 8.16% and 8.24%. It demonstrates that the complex was attached to the surface of the sponge.

### 3.9 The Application of the Hydrophobic Sponge


The superhydrophobic sponge has a potential application in the separation of oil and water. Firstly, the superhydrophobic sponge is compared with the pristine one. Dimethylbenzene, 1, 2-dichloroethane, isocinol and hexane were used as oil phases respectively, and Deionized water as another phase. To mark the oil phase, a little Sudan red is dissolved in it. 20 mL water and 20 mL organic solvent with sudan red were added into a 50 mL beaker, then the superhydrophobic sponge (2 cm×2 cm×1 cm) was fully compacted put at the surface of oil and water. The sponge was taken out from the beaker after the sponge fully absorbed the mixture. In the next step, the liquid in the sponge was squeezed out completely into the measuring cylinder. the oil and water were observed in the measuring cylinder. The result, as shown in Fig. 10, indicates that the pristine sponge shows no obvious selectivity in the separation of oil and water while the superhydrophobic sponge only absorb the oil for the four organic solvents in the investigation.

For some reasons, the wettability of the superhydrophobic sponge will decrease after repeated use. To learn how many times the sponge can be used, the relationship between the contact angle and the number of separation times of oil and water for sponge was studied. Using dimethylbenzene as the oil phase. The process [28] of the study was carried out as show in Fig. 11,(A) Add 50 mL water to a clean beaker;(B).

Add 1 mL dimethylbenzene in the beaker, containing a little sudan red;(C)Put a piece of superhydrophobic sponge (2 cm×2 cm×1 cm) in the beaker to absorb the oil phase.(D)Took the sponge absorbed the oil out the beaker, the water in the beaker was clear without the oil phase;(E)The sponge squeezed out the oil with tweezers and used to absorb the dimethylbenzene again, as described in step C, then repeat D and E; When the number of repetition for the absorption reached 1, 2, 4, 7.....as shown in Fig. 12. In this investigation, the maximum standard deviation and the

average standard deviation of the water contact angles on the sponge are 3.3 and 2.0 separately. The sponge was dried in the oven at 80°C until it evaporated fully, then measured the contact angle to identify its wettability. The result was illustrated in Fig. 12, from the Fig. 12, the water


contact angle decreases from 166° to 153° in the first 11 times and goes down slowly to 150° at the 39 th times, while the repeatability in previous studies was only about 10 times [29,30]. It is believed that the the superhydrophobic sponge can be used for at least 10 times in practice.

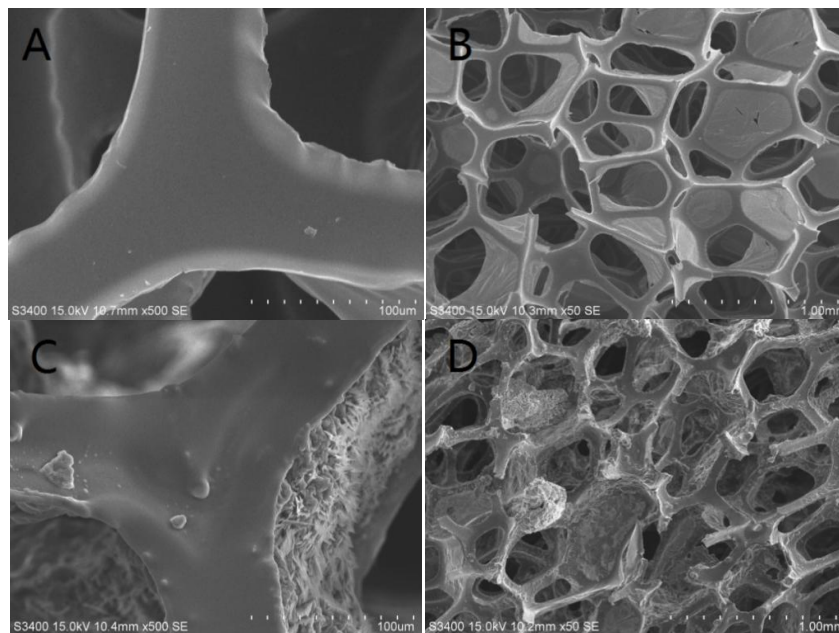


**Fig. 9. SEM analysis of sponge surface**  
(A and B are SEM images of the pristine sponge; C and D are SEM images of superhydrophobic sponge)

**Table 1. EDS for the surface of pristine sponge and superhydrophobic sponge**


Elements	Pristine sponge(Wt%)	Superhydrophobic sponge(Wt%)
C	61.42	71.04
N	9.00	02.83
O	28.63	08.90
Cu	0	08.24
S	0	08.16

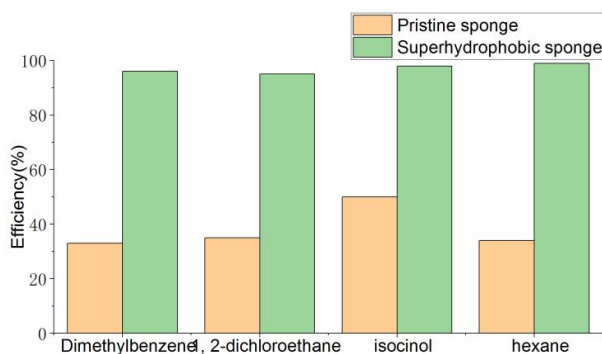

**Fig. 10. The efficiency of pristine and superhydrophobic sponge to absorb the oil phase**

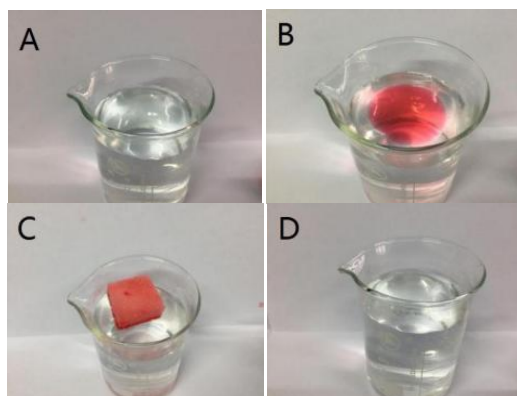

**Fig. 11. The process of oil and water separation**

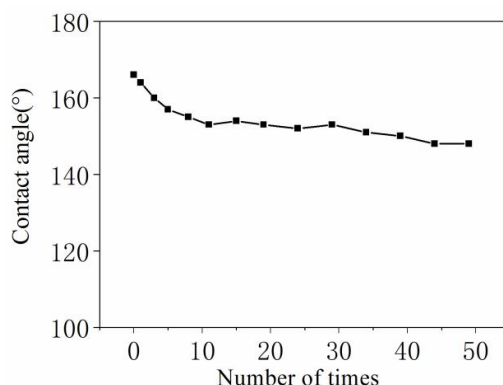

**Fig. 12. Relation between the number of separation and wettability**

#### 4. CONCLUSION

In this paper, a novel superhydrophobic sponge made of complex of 1-dodecanthiol and copper chloride was developed for separation of oil and water. The surface structure and elements of the sponge were identified by SEM and EDS, showing the complex was attached to the sponge surface and increased the surface roughness. The water contact angle on the sponge was measured to characterize its wettability. It was found that the superhydrophobic sponge was developed successfully as indicated by a large water contact angle, which is larger than 150°. The superhydrophobic sponge was studied in application of separation of oil and water. The results show that the developed superhydrophobic sponge only adsorbs the oil phase and demonstrated excellent selectivity for separation of oil and water. The sponge can be used repeatedly up to 39 times. The superhydrophobic sponge developed in the paper have unique advantages, which provides new insights in oil-water separation.

#### COMPETING INTERESTS

Authors have declared that no competing interests exist.

#### REFERENCES

1. Yang Y, Yan L I, Liu G, et al. A hindcast of the Bohai Bay oil spill during June to August 2011 [J]. *Acta Oceanologica Sinica*. 2017;36(11):21-26. DOI:10.1007/s13131-017-1135-7
2. Sugar-Derived Phase-Selective Molecular Gelators as Model Solidifiers for Oil Spills [J]. *Angewandte Chemie*. 2010;122(42):7861-7864. DOI:10.1002/ange.201002 095
3. Abdel-Gawad S, Abdel-Shafy M. Pollution control of industrial wastewater from soap and oil industries: A case study [J]. *Water Science and Technology*. 2002;46(4-5):77-82. DOI:10.2166/wst.2002.0556

4. Wang Q, Cui Z, Xiao Y, et al. Stable highly hydrophobic and oleophilic meshes for oil-water separation [J]. *Applied Surface Science*. 2007;253(23):9054-9060. DOI:10.1016/j.apsusc.2007.05.030
5. Choi HM, Cloud RM. Natural sorbents in oil spill cleanup [J]. *Environmental Science & Technology*. 1992;26(4):772-776. DOI:10.1021/es00028a016
6. Dalton T, Jin D. Extent and frequency of vessel oil spills in US marine protected areas [J]. *Marine Pollution Bulletin*. 2010; 60(11):1935-1945. DOI:10.1016/j.marpolbul.2010.07.036
7. Schaum J, Cohen M, Perry S, et al. Screening level assessment of risks due to dioxin emissions from burning oil from the BP deep water horizon gulf of mexico spill [J]. *Environmental Science and Technology*. 2010;44:(24):9383-9389. DOI:10.1021/es103559w
8. Anastopoulos G. Investigation of the effectiveness of absorbent materials in oil spills clean up [J]. *Desalination*. 2001; 140(3):259-264. DOI:10.1016/S0011-9164(01) 00375-7
9. Xue Z, Cao Y, Liu N, et al. Special Wettable Materials for Oil/Water Separation [J]. *Journal of Materials Chemistry A*. 2014;2(8):2445-2460. DOI:10.1039/C3TA13397D
10. Crick CR, Gibbins JA, Parkin IP. Superhydrophobic polymer-coated copper-mesh; membranes for highly efficient oil-water separation [J]. *Journal of Materials Chemistry A*. 2013;1(19):5943-5948. DOI:10.1039/c3ta10636e
11. Cortese B, Caschera D, Federici F, et al. Superhydrophobic fabrics for oil-water separation through a diamond like carbon (DLC) coating [J]. *Journal of Materials Chemistry A*. 2014;2. DOI:10.1039/C4TA00450G
12. Zhang J, Huang W, Han Y. A Composite Polymer Film with both Superhydrophobicity and Superoleophilicity [J]. *Macromolecular Rapid Communications*. 2006;27(10):804-808. DOI:10.1002/marc.200500842
13. Zhang XX, Wang Y Y, Gu L, et al. Superhydrophobic Surface Modified by Sol-Gel Silica Nanoparticle Coating [J]. *Materials Science Forum*. 2019;960:155-160. DOI:10.4028/www.scientific.net/MSF.960.155
14. Liu K, Yao X, Jiang L. Recent Developments in Bio-Inspired Special Wettability [J]. *Chemical Society Reviews*. 2010;39(8):3240-3255. DOI:10.1039/b917112f
15. Qian C, Chen GH, Yan F, et al. Superhydrophobic characteristics of butterfly wing surface [J]. *Journal of Bionic Engineering*. 2004;1(4):249-255.
16. Nie K, Xu L, Qian T, et al. Fabrication of a Robust and Flame-Retardant Aloo-h-Lignocellulose Composite with a Lotus-Leaf-Like Superhydrophobic Coating [J]. *Journal of Wood Chemistry and Technology*. 2019;1-14. DOI:10.1080/02773813.2019.1654517
17. Wen F, Lei C, Chen J, et al. Hierarchical superhydrophobic surfaces for oil-water separation via a gradient of ammonia content controlling of dopamine oxidative self-olymerization [J]. *Journal of Applied Polymer Science*; 2019. DOI:10.1002/app.48044
18. Chen N, Pan Q. Versatile Fabrication of Ultralight Magnetic Foams and Application for Oil-Water Separation [J]. *ACS Nano*. 2013;7(8):6875-6883. DOI:10.1021/nn4020533
19. Zhang J, Huang W, Han Y. A Composite Polymer Film with both Superhydrophobicity and Superoleophilicity [J]. *Macromolecular Rapid Communications*. 2006;27(10):804-808. DOI:10.1002/marc.200500842
20. Liu Y, Ma J, Wu T, et al. Cost-effective reduced graphene oxide-coated polyurethane sponge as a highly efficient and reusable oil-absorbent [J]. *Applied Materials & Interfaces*. 2013;5(20):10018. DOI:10.1021/am4024252
21. Patankar NA. Transition between Superhydrophobic States on Rough Surfaces [J]. *Langmuir*. 2004;20(17):7097-102. DOI:10.1021/la049329e
22. Zhou X, Zhang Z, Xu X, et al. Facile Fabrication of Superhydrophobic Sponge with Selective Absorption and Collection of Oil from Water [J]. *Industrial & Engineering Chemistry Research*. 2013;52(27):9411-9416. DOI:10.1021/ie400942t
23. Zhang Z, Li Z, Hu Y, et al. Superhydrophobic copper surface fabricated by one-step immersing method in fatty acid salt aqueous solution for excellent anti-



- corrosion and oil/water separation properties [J]. Applied Physics A. 2019;125(8). DOI:10.1007/s00339-019-2843-y
24. Yu CM , Zhuang XH , Zeng SW , et al. Superhydrophobic foam prepared from high internal phase emulsion templates stabilised by oyster shell powder for oil–water separation[J]. RSC Advances. 2019;9. DOI:10.1039/C9RA01258C
25. Bashar MM, Zhu H, Yamamoto S, et al. Superhydrophobic surfaces with fluorinated cellulose nanofiber assemblies for oil–water separation [J]. RSC Advances. 2017;7(59):37168-37174. DOI:10.1039/C7RA06316D
26. Jiang G, Hu R, Xi X, et al. Facile preparation of superhydrophobic and superoleophilic sponge for fast removal of oils from water surface [J]. Journal of Materials Research. 2013;28(4):651-656. DOI:10.1557/jmr.2012.410
27. Yuehuan Wu, Weizhen Li, Xiaoming Shen. Organic Chemistry (Revised Edition). Hefei: Press of University of Science and Technology of China; 2002.
28. Zhang L, Li H, Lai X, et al. Thiolated graphene-based superhydrophobic sponges for oil-water separation[J]. Chemical Engineering Journal. 2017;316: 736-743. DOI:10.1016/j.cej.2017.02.030
29. Saha P, Dashairya L. Reduced graphene oxide modified melamine formaldehyde (rGO@MF) superhydrophobic sponge for efficient oil–water separation [J]. Journal of Porous Materials. 2018;25(5):1475-1488. DOI:10.1007/s10934-018-0560-0
30. Yang X, Shuai Q, Luo Y, et al. Fabrication and Application of the Superhydrophobic Sponge Modified with Poly (dimethylsiloxane) /Silver Micro/Nanoparticles /Polydopamine [J]. Chinese Journal of Applied Chemistry. 2015;32(6): 726-732. DOI:10.11944/j.issn.10000518.2015.06.14 0365

© 2019 Li et al.; This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

*Peer-review history:*

*The peer review history for this paper can be accessed here:  
<http://www.sdiarticle4.com/review-history/53185>*